



CrossMark  
click for updates

Cite this: *RSC Adv.*, 2014, 4, 38182

## High nuclearity Ni(II) cages from hydroxamate ligands†

Cecelia McDonald,<sup>a</sup> Sergio Sanz,<sup>c</sup> Euan K. Brechin,<sup>c</sup> Mukesh Kumar Singh,<sup>d</sup> Gopalan Rajaraman,<sup>\*d</sup> Declan Gaynor<sup>\*b</sup> and Leigh F. Jones<sup>†\*a</sup>

The synthesis, structural and magnetic characterisation of a family of Ni(II) cages built from hydroxamate ligands is presented. Two pentanuclear 12-MC<sub>Ni(II)</sub>-4 metallacrowns [Ni<sub>5</sub>(L<sub>1</sub>)<sub>4</sub>(MeOH)<sub>4</sub>(ClO<sub>4</sub>)<sub>2</sub>·2MeOH (**1**) and [Ni<sub>5</sub>(L<sub>1</sub>)<sub>4</sub>(py)<sub>5</sub>](ClO<sub>4</sub>)<sub>2</sub>·H<sub>2</sub>O (**2**) (where L<sub>1</sub>H<sub>2</sub> = 2-(dimethylamino)phenylhydroxamic acid) share analogous, near-planar {Ni<sub>5</sub>(L<sub>1</sub>)<sub>4</sub>}<sup>2+</sup> cores, but differ in the number and nature of the ligands located at the axial Ni(II) sites; the addition of pyridine converting square planar Ni(II) ions to square-based pyramidal and octahedral Ni(II) ions, introducing extra paramagnetic metal centres which 'switch on' additional magnetic superexchange pathways. Subtle variations in the reaction scheme used to produce complexes **1** and **2** result in both a change of topology and an increase in nuclearity, through isolation of the hepta- and nonametallic complexes [Ni<sub>7</sub>(L<sub>1</sub>H)<sub>8</sub>(L<sub>1</sub>)<sub>2</sub>(H<sub>2</sub>O)<sub>6</sub>](SO<sub>4</sub>)·15H<sub>2</sub>O (**3**), [Ni<sub>9</sub>(μ-H<sub>2</sub>O)<sub>2</sub>(L<sub>2</sub>)<sub>6</sub>(L<sub>2</sub>H)<sub>4</sub>(H<sub>2</sub>O)<sub>2</sub>](SO<sub>4</sub>)·29H<sub>2</sub>O (**4**) and [Ni<sub>9</sub>(μ-H<sub>2</sub>O)<sub>2</sub>(L<sub>2</sub>)<sub>6</sub>(L<sub>2</sub>H)<sub>4</sub>(H<sub>2</sub>O)<sub>2</sub>](ClO<sub>4</sub>)<sub>2</sub>·2MeOH·18H<sub>2</sub>O (**5**) (where L<sub>2</sub>H<sub>2</sub> = 2-(amino)phenylhydroxamic acid). Complementary dc magnetic susceptibility studies and DFT analysis indicate dominant antiferromagnetic exchange interactions in **1**, **2**, **4** and **5**, but competing ferro- and antiferromagnetic exchange in **3**.

Received 21st June 2014  
Accepted 13th August 2014

DOI: 10.1039/c4ra06064d


www.rsc.org/advances

## Introduction

The role of hydroxamic acids (of general formula RCONHOH; Scheme 1) in biology and bioinorganic chemistry cannot be underestimated due to their rich bioactivity originating from their inherent pharmacological, toxicological and pathological properties.<sup>1,2</sup> More specifically these organic acids are able to act as efficient siderophores as well as effective selective enzyme inhibitors for histone deacetylase, ureases and prostaglandin H<sub>2</sub> synthases.<sup>1</sup> Such behaviour stems from their ability to bind strongly to numerous transition metal centres, rendering the catalytic active site impotent in the process and are therefore important ingredients in numerous therapeutic drugs.<sup>1,2</sup> This

chelating ability is also the reason that hydroxamic acids have also been shown to act as effective ligands in the field of coordination chemistry,<sup>3</sup> while industrial application lies in their use in the extraction and subsequent recovery of numerous transition metals (Fe, Co, Ni, Cu, Zn and Cd).<sup>4</sup>

Our own work using the ligands 2-(dimethylamino)phenylhydroxamic acid (L<sub>1</sub>H<sub>2</sub>) and 2-(amino)phenylhydroxamic acid



Scheme 1 Generic molecular structure of the hydroxamic acid ligands used in this work (R = Me; L<sub>1</sub>H<sub>2</sub>; R = H; L<sub>2</sub>H<sub>2</sub>).

<sup>a</sup>School of Chemistry, NUI Galway, University Road, Galway, Ireland. Tel: +353-91-49-3462

<sup>b</sup>Department of Basic Medical Sciences, Royal College of Surgeons in Ireland, Medical University of Bahrain, Adliya, Building No. 2441, Road 2835, Busaiteen 228, PO Box 15503, Kingdom of Bahrain. E-mail: dgaynor@rcsi-mub.com; Tel: +973-17-351450-2300

<sup>c</sup>EaStCHEM School of Chemistry, University of Edinburgh, West Mains Road, Edinburgh, Scotland, EH9 3JJ, UK

<sup>d</sup>Department of Chemistry, Indian Institute of Technology, Powai, Mumbai, 400076, India

† Electronic supplementary information (ESI) available. CCDC 1009473–1009476. For ESI and crystallographic data in CIF or other electronic format see DOI: 10.1039/c4ra06064d

‡ Current address: School of Chemistry, Bangor University, Bangor, Gwynedd, Wales, LL57 2DG, UK. E-mail: leigh.jones@bangor.ac.uk; Tel: +44 (0) 1248-38-2391.

( $L_2H_2$ ) has led to the synthesis of a family of pentametallic 12-MC<sub>Cu(II)</sub>-4 metallacrowns,<sup>5</sup> whose  $\{Cu_5(L_x)_4\}^{2+}$  ( $x = 1, 2$ ) cores could subsequently undergo ligand addition and substitution in a controlled manner towards the premeditated formation of 1- and 2-D extended networks comprising  $\{Cu_5\}$  metallacrown nodes.<sup>6</sup> Herein we present an addition to this work, with the synthesis, structures and magnetic characterisation of a family of novel Ni(II) cages of varying nuclearities and topologies. The 12-MC<sub>Ni(II)</sub>-4 metallacrowns  $[Ni_5(L_1)_4(MeOH)_4](ClO_4)_2 \cdot 2MeOH$  (**1**) and  $[Ni_5(L_1)_4(py)_5](ClO_4)_2 \cdot H_2O$  (**2**) have similar cores, but differ in the number and nature of ligands bonded to the axial sites on the Ni(II) ions, with addition of pyridine converting square planar ( $s = 0$ ) Ni(II) ions in **1** to square-based pyramidal/octahedral Ni(II) ions ( $s = 1$ ) in **2**, introducing additional magnetic superexchange interactions to be “switched on”. Variation in reactions conditions (metal salt, ligand type, base, solvent) leads to both a change in topology to non-metallacrown cages, and an increase in nuclearity from penta- to hepta- and nonametallac.

## Results and discussion

Complex **1** is produced upon reaction of  $Ni(ClO_4)_2 \cdot 6H_2O$ ,  $L_1H_2$  and NaOH in MeOH (see Experimental section for full details), while **2** is made by simply adding pyridine to the same reaction. Systematic variation of the amount of pyridine used did not affect the identity of the isolate product, nor the number of bound pyridine ligands. Complexes **1** and **2** crystallise in the triclinic space group  $P\bar{1}$  and monoclinic space group  $P2_1/n$ , respectively. Pertinent crystallographic data is given in Table 1. Complexes **1** and **2** (Fig. 1) contain near planar  $\{Ni_5(L_1)_4\}^{2+}$  cores, with the central Ni(II) ions (labelled Ni1 in both cases)

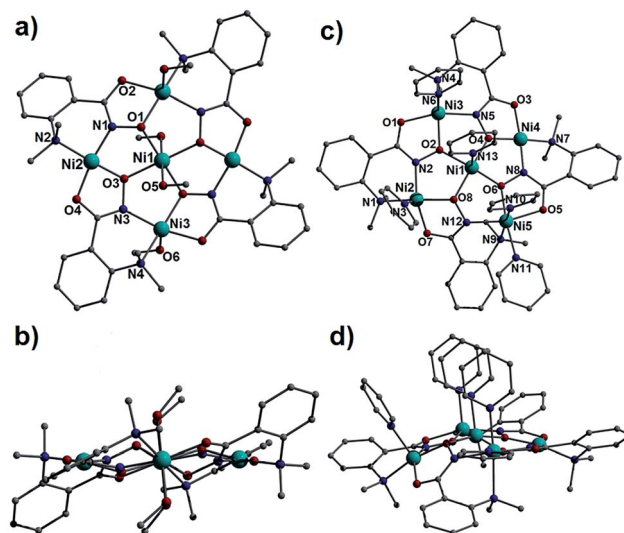


Fig. 1 Crystal structures of **1** and **2** viewed perpendicular (a and c) and parallel (b and d) to their  $\{Ni(II)_5\}$  planar cores. Colour code: light blue (Ni), red (O), dark blue (N), grey (C). The perchlorate counter anions have been omitted for clarity. Hydrogen atoms have been omitted for clarity in all cases.

surrounded by an outer ring or wheel of four Ni(II) centres (Ni2, Ni3 and symmetry equivalent (s.e.) in **1** and Ni2–Ni5 in **2**), themselves connected into a 12-MC-4 metallacrown *via* four doubly deprotonated  $L_1^{2-}$  ligands displaying a  $\eta^1:\eta^2:\eta^1:\eta^1,\mu_3$ -bonding motif (Fig. 1 and S1†). Although analogous in many ways, important structural differences between **1** and **2** lie in the coordination geometries at the metal centres. The central Ni(II) ion in **1** exhibits distorted octahedral geometry, possessing two

Table 1 Crystallographic data for complexes **1**, **2**, **4** and **5**

	<b>1</b> · 2MeOH	<b>2</b> · H <sub>2</sub> O	<b>4</b> · 29H <sub>2</sub> O	<b>5</b> · 2MeOH · 18H <sub>2</sub> O
Formula <sup>a</sup>	C <sub>42</sub> H <sub>64</sub> N <sub>8</sub> O <sub>22</sub> Cl <sub>2</sub> Ni <sub>5</sub>	C <sub>61</sub> H <sub>67</sub> N <sub>13</sub> O <sub>17</sub> Cl <sub>2</sub> Ni <sub>5</sub>	C <sub>70</sub> H <sub>130</sub> N <sub>20</sub> O <sub>57</sub> S <sub>1</sub> Ni <sub>9</sub>	C <sub>74</sub> H <sub>116</sub> N <sub>20</sub> O <sub>52</sub> Cl <sub>2</sub> Ni <sub>9</sub>
M <sub>w</sub>	1397.46	1618.71	2724.19	2716.96
Crystal system	Triclinic	Monoclinic	Orthorhombic	Monoclinic
Space group	$P\bar{1}$	$P2_1/n$	$Ima2$	$Cc$
a/Å	11.191(2)	14.6573(4)	29.1847(11)	20.0036(7)
b/Å	12.389(3)	15.1811(4)	21.2385(7)	25.0628(9)
c/Å	12.401(3)	29.7812(11)	19.7536(6)	21.2234(5)
α/°	70.12(3)	90	90	90
β/°	63.48(3)	93.552(3)	90	90.320(2)
γ/°	64.17(3)	90	90	90
V/Å <sup>3</sup>	1362.0(5)	6614.0(4)	12 244.1(7)	10 640.1(6)
Z	1	4	4	4
T/K	150(2)	150(2)	150(2)	150(2)
λ <sup>b</sup> /Å	0.7107	0.7107	0.7107	0.7107
D <sup>c</sup> /g cm <sup>-3</sup>	1.704	1.624	1.192	1.656
μ(Mo-Kα)/mm <sup>-1</sup>	1.880	1.558	1.431	1.708
Collected/unique, (R <sub>int</sub> ) refl.	10 303/4974, (0.0169)	52 717/12 096, (0.0785)	52 181/11 376, (0.1403)	40 644/16 130, (0.0946)
wR2 (all data)	0.0758	0.11398	0.1531	0.1769
R1 <sup>d,e</sup>	0.0308	0.0482	0.0844	0.0693
Goodness of fit on F <sup>2</sup>	1.024	1.023	0.964	1.027
Flack parameter	n.a	n.a	0.009(18)	0.026(18)

<sup>a</sup> Includes guest molecules. <sup>b</sup> Mo-Kα radiation, graphite monochromator. <sup>c</sup>  $wR2 = [\sum w(|F_o|^2 - |F_c|^2)|^2 / \sum w|F_o|^2]^{1/2}$ . <sup>d</sup> For observed data. <sup>e</sup>  $R1 = \sum ||F_o| - |F_c|| / \sum |F_o|$ .

axially ligated MeOH ligands (Ni1–O5 = 2.153 Å). Two of the four outer metal centres (Ni3 and s.e.) are five coordinate and square based pyramidal, with  $\tau = 0.08$ ,<sup>7</sup> due to the presence of a single axially bound MeOH ligand (Ni3–O6 = 2.036 Å). The remaining two outer Ni(II) centres (Ni2 and s.e.) are not axially ligated, and thus are four coordinate and square planar in geometry. The addition of pyridine leads to different coordination at the Ni(II) centres in **2**. Firstly the central nickel adopts a distorted square-based pyramidal configuration ( $\tau = 0.34$ ) with one axially bound pyridine ligand (Ni1–N13 = 2.012 Å). Likewise the outer ions Ni2 and Ni3 exhibit distorted square pyramidal geometries ( $\tau = 0.34$  and 0.15, respectively), each with one terminal pyridine ligand (Ni2–N3 = 2.029 Å, Ni3–N6 = 2.036 Å). Ni5 is the only six coordinate metal ion, possessing both axially and equatorially bound pyridine ligands (Ni5–N10 = 2.135 Å and Ni5–N11 = 2.090 Å respectively). The effect of this additional pyridine coordination is that the adjacent  $L_1^{2-}$  ligand significantly distorts away from the  $\{Ni_5\}$  plane, forcing it to bond at the axial Ni5 site *via* its  $-NMe_2$  group (Fig. 1). The outer Ni4 ion remains in a four coordinate square planar geometry, suggesting it to be the sole diamagnetic metal centre in **2** (*vide infra*). The axial pyridine ligands coordinated to Ni1, Ni3 and Ni5 appear almost superimposable when viewed along the plane of the molecule, lying at distances typical of  $\pi_{\text{centroid}}-\pi_{\text{centroid}}$  interactions ( $[C_{52}-N_{10}] \cdots [C_{50}-N_{13}] = 3.674$  Å and  $[C_{50}-N_{13}] \cdots [C_{42}-N_6] = 3.651$  Å) (Fig. 1d). Upon close scrutiny of **1** and **2** it becomes apparent that pyridine ligation has promoted a puckering of the  $\{Ni_5\}$  core in **2** when compared to the near planar pentametallike skeleton in **1** (Fig. 1b *cf.* 1d).

The  $\{Ni_5(L_1)_4(MeOH)_4\}^{2+}$  (**1**) and  $\{Ni_5(L_1)_4(py)_5\}^{2+}$  (**2**) cations are each charge balanced by two  $ClO_4^-$  counter anions, sitting above and below the planar  $\{Ni_5\}$  array in **1** and at the periphery of the structure in **2**, the difference presumably due to the presence of the coordinated pyridine ligands (Fig. 2) and subsequent changes to intermolecular interactions. In both cases the O donor atoms of the  $ClO_4^-$  counter anions forge intermolecular H-bonding interactions with nearby  $\{Ni_5\}$  units in all three directions. More specifically the  $ClO_4^-$  units in **1**

hydrogen bond *via* aromatic (*e.g.*  $C_{12}(H_{12}) \cdots O_8 = 2.506$  Å) and aliphatic protons belonging to nearby hydroxamate and terminally bonded MeOH molecules, respectively (*e.g.*  $O_5(H_5H) \cdots O_{10} = 2.445$  Å). Hydrogen bonding is also observed between the terminal and interstitial MeOH molecules (*e.g.*  $O_6(H_6H) \cdots O_{11} = 2.230$  Å). In **2** the predominant H-bonding occurs between the  $ClO_4^-$  counter anions and aromatic hydroxamate protons ( $C_{25}(H_{25}) \cdots O_{13} = 2.584$  Å,  $C_{40}(H_{40}) \cdots O_{16} = 2.590$  Å and  $C_{43}(H_{43}) \cdots O_{14} = 2.585$  Å). The  $\{Ni_5\}$  units in **1** pack in superimposable columns along the *a* cell direction and these stacks are connected through  $\pi-\pi$  stacking interactions between adjacent hydroxamate aromatic rings ( $[C_2-C_7]_{\text{centroid}} \cdots [C_2-C_7]_{\text{centroid}} = 3.897$  Å; Fig. 2, left). The pentametallike cages in **2** arrange themselves into 2D brickwork sheets along the *ab* cell diagonal, with these sheets lying in superimposable rows down *c*, as shown in Fig. 2.

Despite numerous attempts we could not produce the analogous metallacrowns to **1** and **2** using  $L_2H_2$ . The formation of **1** and **2** adds to the relatively small number of 12-MC $_{Ni(II)}$ -4 metallacrowns known in the literature,<sup>8</sup> and are the first constructed using 2-(dimethylamino)phenylhydroxamic acid ( $L_1H_2$ ). Interestingly the general 12-MC $_{Ni(II)}$ -4 framework also appears as a building block within the elaborate and rather unusual fused metallacrown dimer  $Ni(II)_2(mcpa)_2(CH_3OH)_3(H_2O)-[12-MC_{Ni(II)N(shi)2(pk)2-4}][12-MC_{Ni(II)N(shi)3(pk)4}]$  (where  $Hmpca = 2\text{-methyl-4-chlorophenoxyacetic acid}$ ,  $HpkO = di\text{-}(2\text{-pyridyl})\text{-ketone oxime}$  and  $H_3shi = salicylhydroxamic acid$ ).<sup>9</sup>

As previously communicated by one of us,<sup>10</sup> the reaction of  $NiSO_4 \cdot 6H_2O$ ,  $L_1H_2$  in a basic solvent mixture of  $H_2O$  and MeOH gives the heptanuclear complex  $[Ni_7(L_1H)_8(L_1)_2(H_2O)_6](SO_4 \cdot 15H_2O)$  (**3**), a complex whose structure deviates significantly from the metallacrowns of **1** and **2**. The core in **3** (Fig. 3) shows a trigonal bipyramidal array (or alternatively two face-sharing tetrahedra) of nickel(II) ions (Ni2–Ni6) with an extra two metal centres annexed at the apical sites (Ni1 and Ni7). All nickel centres exhibit distorted octahedral geometries and are connected through hydroxamate ligands showing four types of bonding mode ( $\eta^2:\mu-$ ,  $\eta^1:\eta^3:\mu_3-$ ,  $\eta^1:\eta^2:\mu-$  and  $\eta^1:\eta^3:\eta^1:\eta^1:\mu_4$ ; Fig. 3 and S1†). Terminal water molecules complete the coordination spheres at Ni1 and Ni7 (Ni1–O1 = 2.074 Å, Ni7–O5 = 2.090 Å), and at the equatorial Ni3 and Ni5 sites. Intramolecular  $\pi_{\text{centroid}}-\pi_{\text{centroid}}$  interaction at distances of (Å) 3.829 ( $[C_{2B}-C_{7B}] \cdots [C_{2D}-C_{7D}]$ ) and 3.991 ( $[C_{2F}-C_{7F}] \cdots [C_{2K}-C_{7K}]$ ) exist between aromatic rings of nearest neighbour hydroxamate ligands. A single charge balancing  $SO_4^{2-}$  counter anion lies at the periphery of the structure, H-bonding to protons of metal bound  $H_2O$  ligands (*e.g.*  $O_4(H_{4A}) \cdots O_{3SS} = 2.005$  Å) and waters of crystallisation (*e.g.*  $O_{21}(H_{21A}) \cdots O_{1SS} = 1.875$  Å). In the crystal the individual  $\{Ni_7\}$  moieties in **3** arrange into superimposable rows along the *a* cell direction, packing in a brickwork topology in the *bc* plane (Fig. S2†).

The reaction of  $NiSO_4 \cdot 6H_2O$  and  $L_2H_2$  in a basic MeOH– $H_2O$  solution afforded an even larger cage,  $[Ni_9(\mu-H_2O)_2(L_2)_6(L_2H)_4(H_2O)_2](SO_4 \cdot 29H_2O)$  (**4**). Moreover the perchlorate salt of **4**,  $[Ni_9(\mu-H_2O)_2(L_2)_6(L_2H)_4(H_2O)_2](ClO_4)_2 \cdot 2MeOH \cdot 18H_2O$  (**5**) was readily produced using a similar synthetic procedure (see Experimental section for details). Complexes **4** (Fig. S3†) and **5**

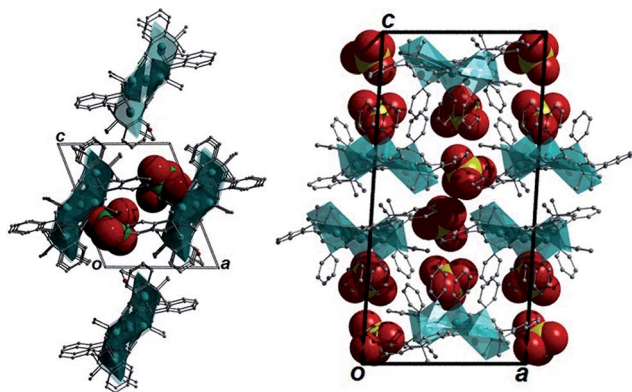


Fig. 2 Packing arrangements of **1** (left) and **2** (right) as viewed down the *b* axis of their respective unit cells. Hydrogen atoms have been omitted for clarity. Perchlorate counter anions are represented in the space-fill mode.

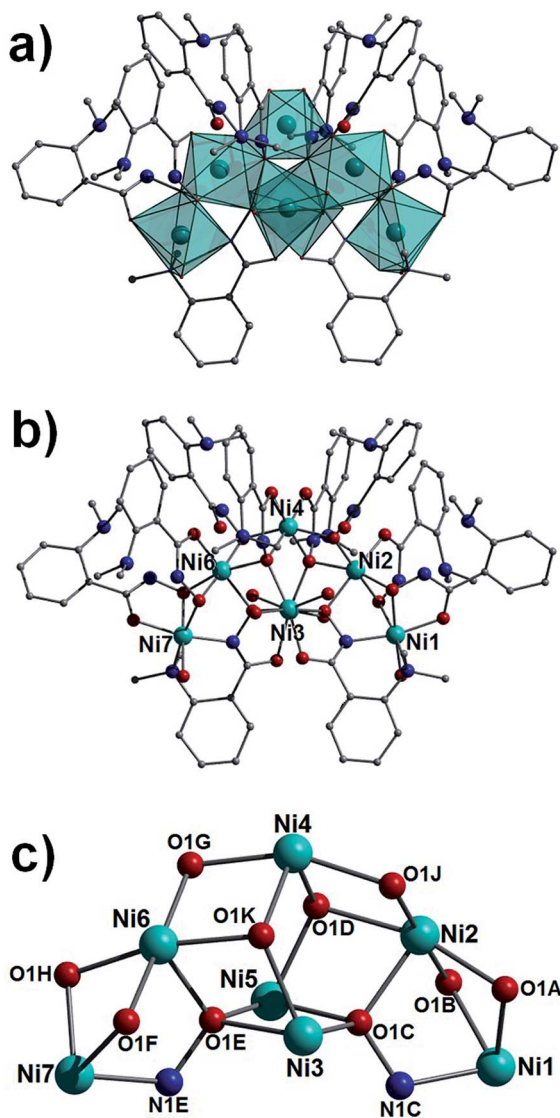


Fig. 3 Polyhedral (a) and regular (b) representation of the crystal structure in 3. (c) Metallic core in 3. Colour code as in Fig. 1. Hydrogen atoms have been omitted for clarity.

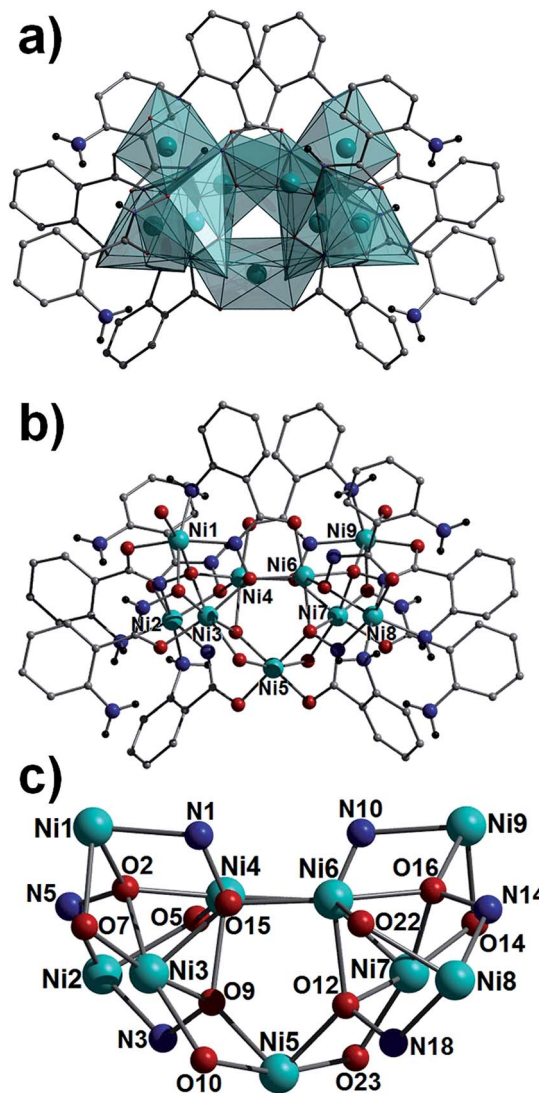


Fig. 4 Polyhedral (a) and regular (b) representation of the crystal structure in 5. (c) The metallic core in 5. Colour code as used in Fig. 1 and elsewhere in the text. The majority of H atoms have been omitted for clarity however the  $-\text{NH}_2$  protons are represented as black spheres.

(Fig. 4) crystallise in the orthorhombic *Ima2* and monoclinic *Cc* space groups, respectively. Pertinent crystallographic details are given in Table 1. The cores in 4 and 5 are best described as comprising two tetrahedral arrays of distorted octahedral Ni(II) ions linked by a single, central, six coordinate Ni(II) metal centre (labelled Ni5 in both cases). The Ni(II) ions are connected by a combination of four singly ( $\text{LH}^-$ ) and six doubly ( $\text{L}^{2-}$ ) deprotonated hydroxamate ligands exhibiting  $\eta^1:\eta^2$ ,  $\mu$ - and  $\eta^1:\eta^3:\eta^1:\eta^1$ ,  $\mu_4$ -bonding modes, respectively (Fig. S1†). In both cases two  $\mu$ -bridging  $\text{H}_2\text{O}$  ligands connect the central Ni5 ion to the tetrahedral units, while terminal water molecules complete the coordination spheres at the two peripheral Ni(II) centres (Ni3–O11 = 2.022 Å in 4; Ni1–O3 = 2.051 Å and Ni9–O17 = 2.042 Å in 5). The resultant  $\{\text{Ni}_9(\mu\text{-H}_2\text{O})_2(\text{L}_2)_6(\text{L}_2\text{H})_4(\text{H}_2\text{O})_2\}^{2+}$  cationic cages are charge balanced by one  $\text{SO}_4^{2-}$  and two  $\text{ClO}_4^-$  counter anions, respectively.

The individual  $\{\text{Ni}_9\}$  units in 4 arrange in the common brickwork motif along the *bc* plane (Fig. 5, left) and are connected to one another *via*  $\pi_{\text{centroid}}-\pi_{\text{centroid}}$  stacking interactions between hydroxamate aromatic rings of neighbouring  $\{\text{Ni}_9\}$  units ( $[\text{C}_8-\text{C}_{13}] \cdots [\text{C}_{15}-\text{C}_{20}] = 3.605$  Å). These sheet-like arrangements stack in superimposable rows along the *a* cell direction to complete the topology in 4 in the crystal (Fig. 5, left). The  $[\text{Ni}_9]$  cages in 5 also arrange themselves in the brickwork motif along the *ac* plane of the unit cell, these 2D sheets stack in a staggered arrangement as opposed to the superimposable rows observed in 4 (Fig. S4†). In a similar fashion to 4,  $\pi_{\text{centroid}}-\pi_{\text{centroid}}$  stacking interactions connect the individual  $[\text{Ni}_9]$  nodes in the brickwork topology ( $[\text{C}_9-\text{C}_{14}] \cdots [\text{C}_{58}-\text{C}_{63}] = 3.538$  Å) and this is aided by numerous H-bonding interactions between aliphatic protons of the hydroxamate ligands ( $-\text{NH}_2$  and  $=\text{NH}$  groups) and waters of crystallisation-effectively acting

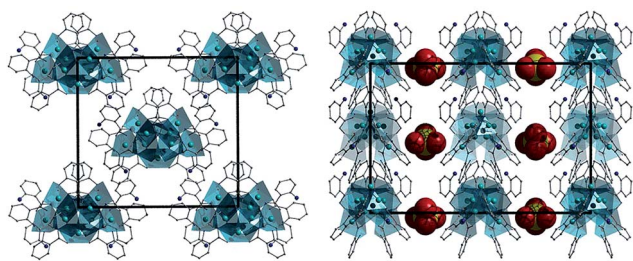


Fig. 5 Crystal packing observed in **4** as viewed along the *a* (left) and *b* (right) cell direction. All hydrogen atoms and solvents of crystallisation have been omitted for clarity. The  $\text{SO}_4^-$  counter anions are represented as space-fill in the figure on the right and removed for clarity on the left.

as molecular mortar in the packing in **5** (*i.e.*  $\text{Ni}17(\text{H}17\text{B})\cdots\text{O}28 = 2.386 \text{ \AA}$ ).

It is somewhat difficult to rationalise the change in structure from **1** and **2** ( $\text{Ni}_5$ ) to **3** ( $\text{Ni}_7$ ), since the reactions involve the use of a different metal salt (perchlorate *versus* sulphate) and different solvent (MeOH *versus* MeOH– $\text{H}_2\text{O}$ ). The difference in reaction schemes between  $[\text{Ni}_5]$  and  $[\text{Ni}_9]$  involve a change in ligand, base and solvent, while the difference in the reaction that produces  $[\text{Ni}_7]$  *versus*  $[\text{Ni}_9]$  is a change in ligand and base. Elucidating the roles of each reaction variable would therefore require a larger library of complexes to be isolated, and we are currently working to that end. However we can say that the role of ligand selection (*i.e.*  $\text{L}_1^{2-}$  in **3** *versus*  $\text{L}_2^{2-}$  in **4**) and more specifically functional group dictated steric effects (Me groups in  $\text{L}_1^{2-}$  *versus* H groups  $\text{L}_2^{2-}$ ) on producing complex **4** over **3** cannot be ignored in terms of structure-directing influences.

### Theoretical determination of paramagnetic centres in complexes **1** and **2**

Complexes **1** and **2** each possess five  $\text{Ni}(\text{II})$  ions displaying a total of three different [distorted] geometries – square planar, square-based pyramidal and octahedral. Square planar  $\text{Ni}(\text{II})$  ions are generally diamagnetic, whereas square-based pyramidal  $\text{Ni}(\text{II})$  ions can be either diamagnetic or paramagnetic depending on the axial ligand strength.<sup>11</sup>  $\text{Ni}(\text{II})$  ions in octahedral environments on the other hand are always paramagnetic in nature. To confirm the electronic structure of these metal ions we have performed DFT calculations employing varying combinations of spin states ( $s = 0$  *versus*  $s = 1$ ) at each of the  $\text{Ni}(\text{II})$  centres in **1** and **2** (Fig. 6). We began by assuming that all the  $\text{Ni}(\text{II})$  ions in complex **1** were paramagnetic ( $s = 1$ ) and then gradually decreased the number of paramagnetic centres while increasing the number of diamagnetic ( $s = 0$ ) metal ions. Five different spin states have been computed for **1** giving rise to triplet ground states for Ni1 (octahedral), Ni3 and Ni3A (square pyramidal). All other configurations outlined in Fig. 6 lie much higher in energy compared to our calculated ground spin state configuration and thus are unlikely to be accessible at ambient conditions; that is, square planar Ni2 and Ni2A have isolated  $s = 0$  ground states and we can conclude that all experimental magnetic properties in **1** are exclusively due to paramagnetic ( $s = 1$ ) ground state configurations at the Ni1, Ni3 and Ni3A

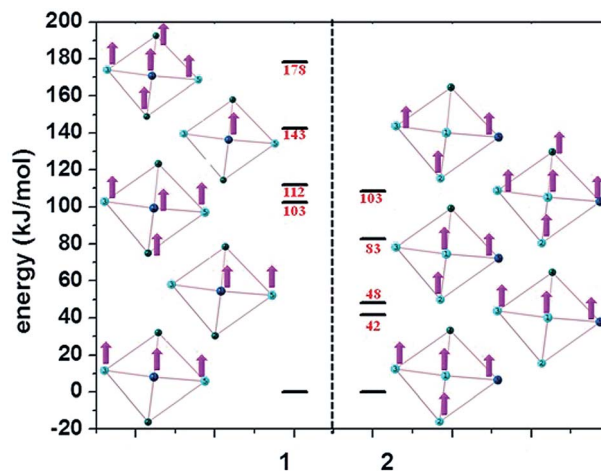


Fig. 6 All possible total spin (*s*) configurations of the individual  $\text{Ni}(\text{II})$  ions in complexes **1** and **2**, with their respective energies ( $\text{kJ mol}^{-1}$ ).

positions. In a similar vein, five different configurations were computed for complex **2**. Here, it was found that Ni(II) centres Ni1, Ni2, Ni3 and Ni5 are paramagnetic ( $s = 1$ ) and square planar Ni4 diamagnetic ( $s = 0$ ), with all other possible configurations lying higher in energy. However unlike complex **1**, these excited state configurations lie somewhat closer than in **1**, with the first excited state lying  $42 \text{ kJ mol}^{-1}$  above the ground state (Fig. 6, right).

### Magnetic susceptibility measurements

Dc magnetic susceptibility measurements were performed on powdered microcrystalline samples of **1–3** and **5** in the 300–5 K temperature range, in an applied field of 0.1 T, and are plotted as their  $\chi_{\text{M}}T$  products in Fig. 7. For the pentametallic species **1** and **2**, the room temperature  $\chi_{\text{M}}T$  values of  $3.55 \text{ cm}^3 \text{ mol}^{-1} \text{ K}$  (**1**) and  $3.43 \text{ cm}^3 \text{ mol}^{-1} \text{ K}$  (**2**) are below that expected for three ( $3.63 \text{ cm}^3 \text{ mol}^{-1} \text{ K}$ ) and four ( $4.84 \text{ cm}^3 \text{ mol}^{-1} \text{ K}$ ) non interacting,

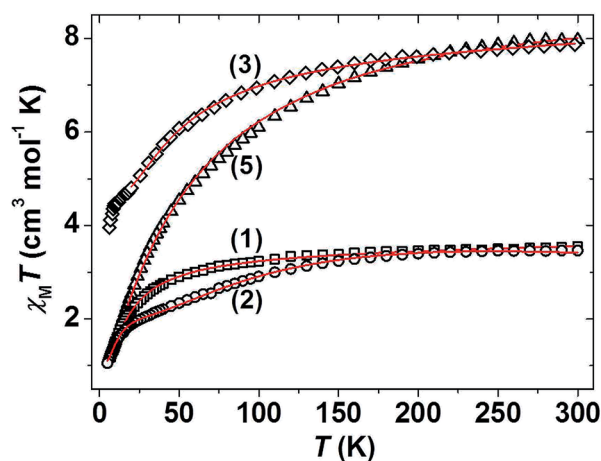


Fig. 7 Plot of  $\chi_{\text{M}}T$  vs.  $T$  for complexes **1** ( $\square$ ), **2** ( $\circ$ ), **3** ( $\diamond$ ) and **5** ( $\triangle$ ). The solid lines represent best-fits of the experimental data. See text for details.

paramagnetic Ni(II) centres, assuming  $g = 2.2$ . Both show a steady decrease in  $\chi_M T$  upon decreasing temperature (although the curve in **2** is steeper than that in **1**), reaching values of 1.28 and 1.10  $\text{cm}^3 \text{mol}^{-1} \text{K}$  at 5 K, respectively. This is indicative of the presence of dominant intramolecular antiferromagnetic interactions in both complexes, with the exchange in **2** being somewhat stronger than in **1**.

For the interpretation of the magnetic properties of **1** and **2** we employed the models given in Fig. 8. Here,  $J_1$  is the isotropic exchange interaction parameter between the central Ni ion and the paramagnetic ions that surround it, mediated by one Ni–O–Ni and one Ni–O–N–Ni interaction;  $J_2$  describes the interaction around the outer ‘wheel’ between the peripheral Ni ions, mediated by one Ni–O–N–Ni interaction.<sup>12</sup> The best-fit parameters obtained were  $J_1 = -3.51 \text{ cm}^{-1}$  (**1**) and  $J_1 = -16.87 \text{ cm}^{-1}$  and  $J_2 = -7.83 \text{ cm}^{-1}$  (**2**). The ground state of **1** is an  $S = 1$  state, and the ground state in **2** is also an  $S = 1$  state, but with an  $S = 0$  state just 1.43  $\text{cm}^{-1}$  above (Fig. 9). The individual Ni–O<sub>oximate</sub>–Ni magnetic pathways in **1** (Ni1–O1–Ni3 = 103.98°) and **2** (Ni1–O8–Ni2 = 113.85°, Ni1–O2–Ni3 = 120.54° and Ni1–O6–Ni5 = 115.18°) each lie in the range expected for mediating antiferromagnetic exchange, with larger angles mediating stronger interactions as observed experimentally.<sup>13,14</sup>

Magnetic susceptibility studies on complex **5** also show the presence of dominant antiferromagnetic exchange between the Ni(II) centres (Fig. 7), but the data for complex **3** suggests more competition between ferro- and antiferromagnetic exchange. The room temperature  $\chi_M T$  values of 7.87 and 7.98  $\text{cm}^3 \text{mol}^{-1} \text{K}$ , respectively, are below the values expected for seven and nine

non-interacting paramagnetic Ni(II) ions (8.47 (**3**) and 10.89 (**5**)  $\text{cm}^3 \text{mol}^{-1} \text{K}$ , assuming  $g = 2.2$ ). For complex **5**, the value decreases monotonically with decreasing temperature, reaching 1.14  $\text{cm}^3 \text{mol}^{-1} \text{K}$  at  $T = 5 \text{ K}$ . The variable  $T$  data for **3** are a little more complex. The  $\chi_M T$  product decreases steadily but slowly to approximately  $T = 25 \text{ K}$  where it then plateaus at a value of  $\sim 4.5 \text{ cm}^3 \text{mol}^{-1} \text{K}$ , before decreasing again at lower temperatures, reaching a minimum value of 3.95  $\text{cm}^3 \text{mol}^{-1} \text{K}$ . The structural complexity of **3** and **5** precludes detailed quantitative analyses of the susceptibility data, since there are numerous different exchange interactions. However, the magnitude of the exchange can be estimated through the employment of simple models. In each case we attempted to fit the susceptibility with just one  $J$  value, assuming all Ni···Ni interactions to be of similar magnitude. This approach was successful for complex **5** and afforded  $J_1 = -5.27 \text{ cm}^{-1}$  with  $g$  fixed to 2.2. For complex **3**, this approach did not work and two  $J$  values were required (Fig. S5†); one ( $J_1$ ) to describe Ni ions connected by a one-atom (Ni–O–Ni) bridge, and one ( $J_2$ ) to describe Ni ions connected by two-atom (Ni–O–N–Ni) bridges. This afforded the best fit parameters  $J_1 = +0.64 \text{ cm}^{-1}$  and  $J_2 = -8.94 \text{ cm}^{-1}$  (**3**) with  $g$  fixed to 2.2. These numbers are a guide only, but are similar to structurally similar Ni(II) cages previously reported in the literature.<sup>13,14</sup>

### Theoretical studies of the magnetic exchange in complexes **1** and **2**

DFT studies were carried out to compute the intramolecular magnetic exchange coupling in complexes **1** and **2**. More specifically we computed the energies of four different spin configurations to obtain two exchange coupling constants corresponding to the ground state in **1** (see Table S1† for all computed configurations). Since complex **2** is asymmetric, five independent  $J$  values were computed using seven different spin configurations (see Table S2† for all computed configurations). The corresponding Hamiltonians for **1** and **2** are given in the computational details section and all computed magnetic coupling constants calculated for complex **1** and **2** are shown in Fig. 10.

Calculations on complex **1** yielded weak antiferromagnetic  $J$  values ( $J_{1A} = J_{1B} = -0.4 \text{ cm}^{-1}$ ) in agreement with those obtained experimentally, albeit somewhat smaller in magnitude. The computed spin density plot for the high spin configuration (an  $S = 3$  state) in **1** is shown in Fig. 11 and clearly shows dominant

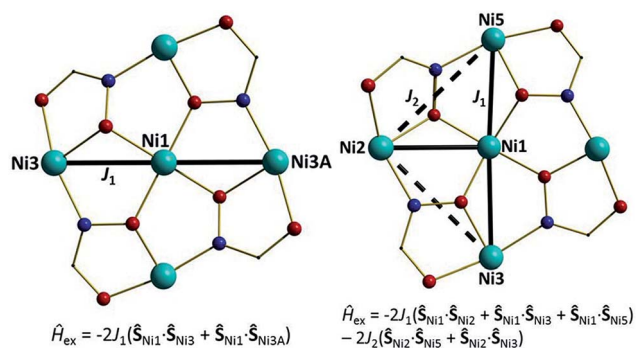


Fig. 8 Schematic illustrating the models used to fit the experimental data for complexes **1** and **2**. See main text for fitting parameters.

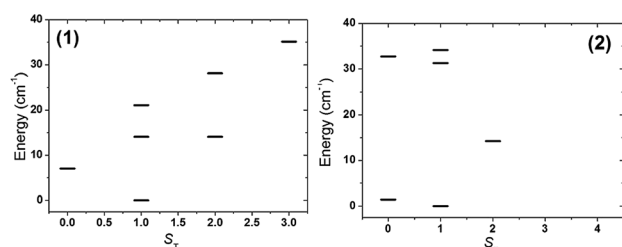


Fig. 9 Energy versus total spin state for the lowest lying  $S$  states in **1** and **2** as determined from the isotropic fit of the susceptibility data.

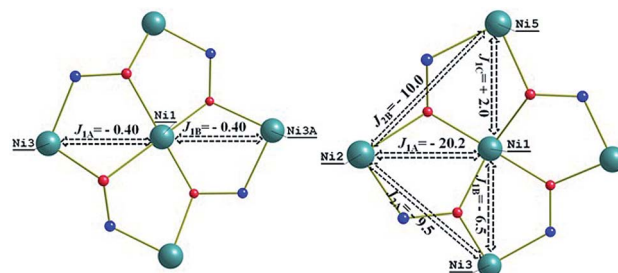


Fig. 10 Schematic representation of the magnetic coupling constants (in  $\text{cm}^{-1}$ ) in **1** (left) and **2** (right).

spin delocalization leading to AF coupling. Computed overlap integrals support this argument where significant overlap between  $d_{x^2-y^2}$  orbitals is detected (see Table S3† for details).

Calculations carried out on complex **2** again reveal that  $J_2 = J_{2A} = J_{2B}$  and that the experimental ( $J_2 = -7.83 \text{ cm}^{-1}$ ) and theoretical ( $J_{2A} = -9.5 \text{ cm}^{-1}$  and  $J_{2B} = -10.0 \text{ cm}^{-1}$ ) values are very similar in magnitude. The computed  $J_1$  values ( $J_{1A-C}$ ) suggest the presence of a range of exchange types, from weakly ferromagnetic ( $J_{1C} = +2.0 \text{ cm}^{-1}$ ) to strongly antiferromagnetic ( $J_{1A} = -20.2 \text{ cm}^{-1}$ ), somewhat in contrast to that derived from experiment ( $J_1 = -16.37 \text{ cm}^{-1}$ ). The  $J_{1A-C}$  exchange interactions in complex **2** are mediated *via* a combination of Ni–O<sub>oximate</sub>–Ni and Ni–N–O–Ni moieties, while the  $J_{2A}$  and  $J_{2B}$  are mediated *via* NO bridges only. Interestingly all calculated  $J$  values were shown to be AF in nature apart from (ferromagnetic)  $J_{1C}$ , which arises from the inherent orthogonality of the  $d_{x^2-y^2}$  orbitals belonging to Ni1 and Ni5. The orthogonality arises from the relatively acute Ni1–O6–Ni5 angle ( $115.18^\circ$ ) and the large Ni1–O8–Ni12–Ni5 dihedral twist ( $31.58^\circ$ ) observed along the Ni1⋯Ni5 pathway (Fig. 12 and Table S5†).

The dominant magnetic interaction in both  $[\text{Ni}_5]$  complexes occurs in the plane of the molecule, and the relative (albeit small) differences in the exchange interactions between complexes **1** and **2** can be explained and visualised through the orientations of their molecular orbitals. While all paramagnetic Ni(II) ions in complex **1** have their  $d_{x^2-y^2}$  orbitals in the  $\{\text{Ni}_5\}$  plane, Ni5 in complex **2** does not; here the  $d_{z^2}$  orbital lies in the

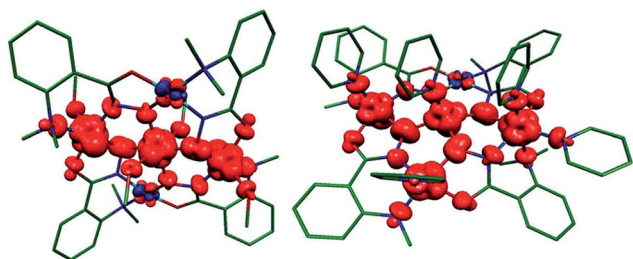


Fig. 11 DFT computed spin density plots for complex **1** (left) and **2** (right). Here red and blue indicates positive and negative spin densities respectively.

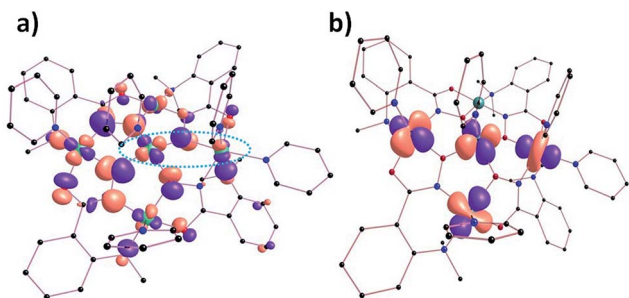


Fig. 12 (a) One of the MOs of complex **2** highlighting orthogonality between the  $d_{x^2-y^2}$  magnetic orbitals of centres Ni1 and Ni5 respectively (circled). (b) Natural hybrid orbitals<sup>15</sup> representing the dominant orbital interactions in the molecular plane of complex **2** (see ESI Table S4† for computed overlap integral values).

plane (Fig. 12b). The AF magnetic pathways in **2** arise because of significant overlap between the  $d_{x^2-y^2}$  and  $d_{x^2-y^2}/d_{z^2}$  magnetic orbitals as shown in Fig. 12b. Likewise, a significant  $d_{x^2-y^2}|p|d_{x^2-y^2}$  overlap along the Ni1⋯Ni2 vector was detected, supporting a strong antiferromagnetic  $J_{1A}$  (see Table S4†). The spin density plot shown in Fig. 11 reveals that a dominant spin delocalization mechanism is operative in **2**, with larger spin densities residing on the O-atoms.

### Concluding remarks

The hydroxamic acids 2-(dimethylamino)phenylhydroxamic acid ( $L_1H_2$ ) and 2-(amino)phenylhydroxamic acid ( $L_2H_2$ ) have been successfully used as bridging ligands in the synthesis of a family of Ni(II) cages ranging from penta- to nonametallacrown. Addition of pyridine to the reaction mixture that produces the 12-MC<sub>Ni(II)</sub>-4 metallacrown  $[\text{Ni}_5(L_1)_4(\text{MeOH})_4](\text{ClO}_4)_2 \cdot 2\text{MeOH}$  (**1**) leads to additional axial ligation at some Ni(II) centres, forming the related metallacrown  $[\text{Ni}_5(L_1)_4(\text{py})_5](\text{ClO}_4)_2 \cdot 1\text{H}_2\text{O}$  (**2**), converting square planar sites to square-based pyramidal/octahedral sites, 'switching on' additional magnetic superexchange pathways. DFT analysis computed triplet  $s = 1$  ground states for the latter two geometries. Structural rearrangement to non-metallacrown topologies can be achieved through simple variation in reaction conditions, leading to the formation of the hepta and nonametallacrown cages  $[\text{Ni}_7(L_1H)_8(L_1)_2(\text{H}_2\text{O})_6](\text{SO}_4) \cdot 15\text{H}_2\text{O}$  (**3**),  $[\text{Ni}_9(\mu\text{-H}_2\text{O})_2(L_2)_6(L_2H)_4(\text{H}_2\text{O})_2](\text{SO}_4) \cdot 29\text{H}_2\text{O}$  (**4**) and  $[\text{Ni}_9(\mu\text{-H}_2\text{O})_2(L_2)_6(L_2H)_4(\text{H}_2\text{O})_2](\text{ClO}_4)_2 \cdot 2\text{MeOH} \cdot 18\text{H}_2\text{O}$  (**5**), which display metallic skeletons comprising two bi-capped, face-sharing tetrahedra in **3** and two annexed tetrahedra in **4** and **5**. The linear arrangement of three antiferromagnetically coupled Ni(II) centres in **1** leads to a  $S = 1$  ground state. Dominant antiferromagnetic exchange is also present in complexes **2** and **5**, but competing ferro- and antiferromagnetic exchange between the seven nickel centres in complex **3** leads to the stabilisation of an intermediate ground spin state. DFT calculations were employed to ascertain the electronic structure of the Ni(II) centres in complexes **1** and **2**, confirming the presence of three and four paramagnetic,  $s = 1$ , Ni(II) centres, respectively. DFT computed magnetic exchange interactions nicely reflect experimental observations, and overlap between the magnetic orbitals can be employed to rationalise the nature and magnitude of the interactions.

### Experimental section

Infra-red spectra were recorded on a Perkin Elmer FT-IR *Spectrum One* spectrometer equipped with a Universal ATR Sampling accessory (NUI Galway). Elemental analysis was carried out at the School of Chemistry microanalysis service at NUI Galway. Variable-temperature, solid-state direct current (dc) magnetic susceptibility data down to 5 K were collected on a Quantum Design MPMS-XL SQUID magnetometer equipped with a 7 T dc magnet. Diamagnetic corrections were applied to the observed paramagnetic susceptibilities using Pascal's constants.

### Crystal structure information

Complex **3** was originally collected and published elsewhere (CCDC no.: 175223).<sup>10</sup> The structures of **1**, **2**, **4** and **5** (CCDC numbers 1009473–1009476) were collected on an Xcalibur S single crystal diffractometer (Oxford Diffraction) using an enhanced Mo source. Each data reduction was carried out on the CrysAlisPro software package. The structures were solved by direct methods (SHELXS-97)<sup>16</sup> and refined by full matrix least squares using SHELXL-97.<sup>17</sup> SHELX operations were automated using the OSCAIL software package.<sup>18</sup> All hydrogen atoms in **1**–**5** were assigned to calculated positions. All non-hydrogen atoms were refined anisotropic with the exception of the sulphate and perchlorate anions in **4** and **5** respectively, which remained isotropic. One of the two ClO<sub>4</sub><sup>−</sup> counter anions in **5** (labelled Cl1–O50–O53) was restrained using the DFIX command. A DFIX restraint was also required for the S1–O15 bond in the SO<sub>4</sub><sup>2−</sup> anion in **4**. Residual electron density in solvent accessible voids and channels were observed in **4** and so were modelled using the SQUEEZE program.<sup>19</sup> The two large channels (total voids volume ~1143 Å<sup>3</sup>) in **4** contained extremely diffuse electron density and were assumed to contain numerous waters of crystallisation. CHN analysis on **4** supported these observations. Although the PLATON program suggests the orthorhombic *Aba2* space group for the structure in **5** and despite our best efforts, no plausible structural solution was obtained.

### Computational details

DFT studies were performed on complexes **1** and **2** to predict the ground spin state of each individual Ni(II) ion and to ascertain the exchange coupling constants between ions. The calculations were performed using the Gaussian 09 suite of programmes.<sup>20</sup> We used the hybrid B3LYP function<sup>21</sup> along with a TZV<sup>22</sup> basis set for Ni(II) and all other elements. Density Functional Theory along with broken symmetry<sup>23</sup> has been shown to be a reliable tool for computing exchange coupling. For systems with two paramagnetic centres, the energy difference between the high and low spin configurations will yield a magnetic coupling constant (*J*). However since we are dealing with pentametallic systems the number of possible configurations is greater (2<sup>*n*</sup>/2; where *n* = number of paramagnetic centres). For complexes **1** and **2** we have used the spin Hamiltonians in eqn (1) (**1**) and (2), which correspond to the model scheme in Fig. 10.

$$\hat{H} = -2J_{1A}(\hat{S}_1 \cdot \hat{S}_3) - 2J_{1B}(\hat{S}_1 \cdot \hat{S}_{3A}) \quad (1)$$

$$\begin{aligned} \hat{H} = & -2J_{1A}(\hat{S}_1 \cdot \hat{S}_2) - 2J_{1B}(\hat{S}_1 \cdot \hat{S}_3) - 2J_{2A}(\hat{S}_2 \cdot \hat{S}_3) \\ & - 2J_{2B}(\hat{S}_2 \cdot \hat{S}_5) - 2J_{1C}(\hat{S}_1 \cdot \hat{S}_5) \end{aligned} \quad (2)$$

here the *J<sub>i</sub>* (*i* = 1–3A in **1**; *i* = 1–5 in **2**) values are the isotropic exchange coupling constants, *S<sub>i</sub>* the spin moment on the Ni(II) centres.

### Preparation of complexes

All reactions were performed under aerobic conditions and all reagents and solvents were used as purchased. **Caution:** although no problems were encountered in this work, care

should be taken when manipulating the potentially explosive perchlorate salts. 2-(Dimethylamino)phenylhydroxamic acid (L<sub>1</sub>H<sub>2</sub>) and 2-(amino)phenylhydroxamic acid (L<sub>2</sub>H<sub>2</sub>) were synthesised using previously reported synthetic procedures.<sup>24</sup>

[Ni<sub>5</sub>(L<sub>1</sub>)<sub>4</sub>(MeOH)<sub>4</sub>](ClO<sub>4</sub>)<sub>2</sub>·2MeOH (**1**). Ni(ClO<sub>4</sub>)<sub>2</sub>·6H<sub>2</sub>O (0.2 g, 0.55 mmol), L<sub>1</sub>H<sub>2</sub> (0.1 g, 0.55 mmol) and NaOH (0.022 g, 0.55 mmol) were dissolved in 30 cm<sup>3</sup> of MeOH and stirred for 2 h. The green solution obtained was filtered and X-ray quality crystals were obtained upon slow evaporation of the mother liquor, and from diffusion of Et<sub>2</sub>O into the mother liquor. Crystals of **1** were collected and air dried, with a yield of approximately 14%. Elemental analysis (%) calculated as [Ni<sub>5</sub>(L<sub>1</sub>)<sub>4</sub>(MeOH)<sub>2</sub>](ClO<sub>4</sub>)<sub>2</sub>·5H<sub>2</sub>O (C<sub>38</sub>H<sub>58</sub>Cl<sub>2</sub>N<sub>8</sub>O<sub>23</sub>Ni<sub>5</sub>): C 33.58, H 4.30, N 8.24. Found: C 33.36, H 4.30, N 8.24. FT-IR (cm<sup>−1</sup>): 3511(w), 1591(s), 1559(m), 1465(w), 1373(m), 1279(w), 1084(s), 1014(m), 936(m), 910(m), 777(m), 704(m), 688(m), 676(m), 663(s).

[Ni<sub>5</sub>(L<sub>1</sub>)<sub>4</sub>(py)<sub>5</sub>](ClO<sub>4</sub>)<sub>2</sub>·H<sub>2</sub>O (**2**). Ni(ClO<sub>4</sub>)<sub>2</sub>·6H<sub>2</sub>O (0.25 g, 0.68 mmol), L<sub>1</sub>H<sub>2</sub> (0.12 g, 0.68 mmol) and NaOH (0.027 g, 0.68 mmol) were dissolved in 35 cm<sup>3</sup> of MeOH. After 5 minutes 1 cm<sup>3</sup> (12.4 mmol) of pyridine was added and the solution stirred for a further 2 h. The resultant green solution was filtered and X-ray quality crystals of **2** were obtained upon slow evaporation of the mother liquor. Crystals of **2** were also obtained by diffusing Et<sub>2</sub>O into the mother liquor. Both batches of **2** were collected and air dried with a yield of approximately 10%. Elemental analysis calculated (%) for [Ni<sub>5</sub>(L<sub>1</sub>)<sub>4</sub>(py)<sub>5</sub>](ClO<sub>4</sub>)<sub>2</sub>·3H<sub>2</sub>O (C<sub>61</sub>H<sub>71</sub>Cl<sub>2</sub>N<sub>13</sub>O<sub>19</sub>Ni<sub>5</sub>): C 44.28, H 4.33, N 11.00. Found: C 44.01, H 4.22, N 10.99. FT-IR (cm<sup>−1</sup>): 2990(w), 1590(m), 1566(w), 1541(m), 1486(w), 1467(w), 1447(m), 1375(m), 1284(w), 1218(w), 1147(w), 1082(s), 1028(m), 1014(m), 946(m), 918(m), 784(w), 765(m), 751(m), 704(m), 689(s), 673(m), 662(m).

[Ni<sub>7</sub>(L<sub>1</sub>H)<sub>8</sub>(L<sub>1</sub>)<sub>2</sub>(H<sub>2</sub>O)<sub>6</sub>](SO<sub>4</sub>)·15H<sub>2</sub>O (**3**). L<sub>1</sub>H<sub>2</sub> (0.25 g, 1.4 mmol) in 20 cm<sup>3</sup> of methanol was added to a solution of NiSO<sub>4</sub>·6H<sub>2</sub>O (0.46 g, 1.76 mmol) in 40 cm<sup>3</sup> of water. The pH of the resulting solution was raised to 6.1 by addition of 0.2 M NaOH before being left to stand at 4 °C for 48 hours. The resulting light green semi-crystalline product was filtered and dried before recrystallisation from methanol and water (1 : 1). The resulting green crystalline solid of **3** was filtered, washed with methanol and air dried with a yield of approximately 40%. Elemental analysis calculated (%) for [Ni<sub>7</sub>(L<sub>1</sub>H)<sub>8</sub>(L<sub>1</sub>)<sub>2</sub>(H<sub>2</sub>O)<sub>6</sub>](SO<sub>4</sub>)·15H<sub>2</sub>O (C<sub>90</sub>H<sub>150</sub>N<sub>20</sub>O<sub>45</sub>SNi<sub>7</sub>): C 40.39, H 5.67, N 10.47. Found: C 39.98, H 5.32, N 10.19. FT-IR (cm<sup>−1</sup>): 2987(s), 2795(s) 1608(s) 1562(s), 1289(m).

[Ni<sub>9</sub>(μ-H<sub>2</sub>O)<sub>2</sub>(L<sub>2</sub>)<sub>6</sub>(L<sub>2</sub>H)<sub>4</sub>(H<sub>2</sub>O)<sub>2</sub>](SO<sub>4</sub>)·29H<sub>2</sub>O (**4**). Ni(SO<sub>4</sub>)·6H<sub>2</sub>O (0.25 g, 0.95 mmol), L<sub>2</sub>H<sub>2</sub> (0.15 g, 0.95 mmol) and NET<sub>4</sub>OH (0.7 cm<sup>3</sup>, 0.72 g, 4.89 mmol) were dissolved in 40 cm<sup>3</sup> of a 1 : 1 MeOH : H<sub>2</sub>O solution. The solution was stirred for 4 h resulting in a green solution which was then filtered and allowed to stand. Upon slow evaporation green X-ray quality crystals of **4** formed after a few days. The crystals were collected and air dried with a yield of approximately 11%. Elemental analysis (%) calculated for as [Ni<sub>9</sub>(μ-H<sub>2</sub>O)<sub>2</sub>(L<sub>2</sub>)<sub>6</sub>(L<sub>2</sub>H)<sub>4</sub>(H<sub>2</sub>O)<sub>2</sub>](SO<sub>4</sub>)·12H<sub>2</sub>O (C<sub>70</sub>H<sub>96</sub>N<sub>20</sub>O<sub>40</sub>S<sub>1</sub>Ni<sub>9</sub>): C 34.77, H 4.00, N 11.59. Found: C 35.14, H 3.61, N 11.40. FT-IR (cm<sup>−1</sup>): 3200(w), 1583(m), 1547(s),



1492(m), 1450(w), 1373(m), 1152(w), 1080(m), 1017(m), 935(w), 903(m), 819(w), 747(s), 692(m), 670(s).

$[\text{Ni}_9(\mu\text{-H}_2\text{O})_2(\text{L}_2)_6(\text{L}_2\text{H})_4(\text{H}_2\text{O})_2](\text{ClO}_4)_2 \cdot 2\text{MeOH} \cdot 18\text{H}_2\text{O}$  (5).  $\text{Ni}(\text{ClO}_4)_2 \cdot 6\text{H}_2\text{O}$  (0.25 g, 0.68 mmol),  $\text{L}_2\text{H}_2$  (0.10 g, 0.68 mmol) and  $\text{NEt}_4\text{OH}$  (0.7 cm<sup>3</sup>, 0.72 g, 4.89 mmol) were dissolved in 40 cm<sup>3</sup> of a 1 : 1 MeOH :  $\text{CH}_3\text{CN}$  solution. The solution was stirred for 4 h resulting in a green solution which was filtered and evaporated to dryness. The green solid was subsequently redissolved in 20 cm<sup>3</sup> of a 1 : 1 MeOH :  $\text{H}_2\text{O}$  solution and stirred for a further 2 h. The resultant green solution was filtered and X-ray quality crystals of 5 were obtained upon slow evaporation of the reaction mixture in 10% yield. Elemental analysis calculated (%) for  $[\text{Ni}_9(\mu\text{-H}_2\text{O})_2(\text{L}_2)_6(\text{L}_2\text{H})_4(\text{H}_2\text{O})_2](\text{ClO}_4)_2 \cdot 20\text{H}_2\text{O}$  ( $\text{C}_{70}\text{H}_{112}\text{N}_{20}\text{O}_{52}\text{Cl}_2\text{Ni}_9$ ): C 31.55, H 4.24, N 10.51. Found: C 31.82, H 3.92, N 10.25. FT-IR (cm<sup>-1</sup>): 3203(m), 1611(m), 1583(m), 1547(s), 1494(m), 1450(w), 1374(m), 1153(m), 1091(m), 1014(m), 936(m), 903(s), 869(w), 819(w), 749(s), 694(m), 671(s).

## Acknowledgements

The authors would like to thank the College of Science, NUI Galway for their support (CM). EKB would like to thank the EPSRC for funding (SS). GR acknowledges financial support from the Government of India through the Department of Science and Technology (SR/S1/IC-41/2010; SR/NM/NS-1119/2011) and generous computational resources from the Indian Institute of Technology-Bombay. MKS thanks the University Grants Commission for a Junior Research Fellowship.

## References

- (a) D. Griffith, M. Devocelle and C. J. Marmion, *Hydroxamic Acids: Their Chemistry, Bioactivity, Solution and Solid Phase Synthesis in Amino Acids, Peptides and Proteins in Organic Chemistry*, ed. A. B. Hughes, 2009, vol. 2, pp. 93–137; (b) M. Paris, M. Porcelloni, M. Binaschi and D. Fattori, *J. Med. Chem.*, 2008, **51**, 1505; (c) Z. Amtul, R. Attaur, R. A. Siddiqui and M. I. Choudhary, *Curr. Med. Chem.*, 2002, **9**, 1323–1348; (d) D. T. Puerta and S. M. Cohen, *Curr. Top. Med. Chem.*, 2004, **4**, 1551.
- (a) E. M. F. Muri, M. J. Nieto, R. D. Sindelar and J. S. Williamson, *Curr. Med. Chem.*, 2002, **9**, 1631–1653; (b) C. J. Marmion, D. Griffith and K. B. Nolan, *Eur. J. Inorg. Chem.*, 2004, **2004**, 3003.
- R. Codd, *Coord. Chem. Rev.*, 2008, **252**, 1387–1408.
- (a) A. M. Wilson, P. J. Bailey, P. A. Tasker, J. R. Turkington, R. A. Grant and J. B. Love, *Chem. Soc. Rev.*, 2014, **43**, 123–134; (b) B. K. Tait, K. E. Mdalose and I. Taljaard, *Hydrometallurgy*, 1995, **38**, 1–6.
- For an extensive review on metallocrowns see: G. Mezei, C. M. Zaleski and V. L. Pecoraro, *Chem. Rev.*, 2007, **107**, 4933.
- C. McDonald, T. Whyte, S. M. Taylor, S. Sanz, E. K. Brechin, D. Gaynor and L. F. Jones, *CrystEngComm*, 2013, **15**(34), 6672–6681.
- A. W. Addison, T. N. Rao, J. Reedijk, J. van Rijn and G. C. Verschoor, *J. Chem. Soc., Dalton Trans.*, 1984, 1349–1356.
- (a) Z. Chen, M. Jia, Z. Zhang and F. Liang, *Cryst. Growth Des.*, 2010, **10**(11), 4806–4814; (b) M. Alexiou, I. Tsvikas, C. Dendrinou-Samara, A. A. Pantazaki, P. Trikalitis, N. Lalioti, D. A. Kyriakidis and D. P. Kessissoglou, *J. Inorg. Biochem.*, 2003, **93**, 256–264; (c) G. Psomas, A. J. Stemmler, C. Dendrinou-Samara, J. J. Bodwin, M. Schneider, M. Alexiou, J. W. Kampf, D. P. Kessissoglou and V. L. Pecoraro, *Inorg. Chem.*, 2001, **40**, 1562–1570; (d) D. Bacco, V. Bertolasi, F. Dellavalle, L. Galliera, N. Marchetti, L. Marchio, M. Remelli and M. Tegoni, *Dalton Trans.*, 2011, **40**, 2491–2501.
- G. Psomas, C. Dendrinou-Samara, M. Alexiou, A. Tsohos, C. P. Raptopoulou, A. Terzis and D. P. Kessissoglou, *Inorg. Chem.*, 1998, **37**, 6556–6557.
- D. Gaynor, Z. A. Starikova, S. Ostrovsky, W. Haase and K. B. Nolan, *Chem. Commun.*, 2002, 506.
- For examples of diamagnetic square based pyramidal Ni(II) complexes see: (a) A. F. Kolodziej, *Prog. Inorg. Chem.*, 1994, **41**, 493; (b) M. A. Halcrow and G. Christou, *Chem. Rev.*, 1994, **94**, 2421; (c) J. J. Wilker, A. Gelasco, M. A. Pressler, R. O. Day and M. J. Maroney, *J. Am. Chem. Soc.*, 1991, **113**, 6324; (d) M. Cha, C. L. Gatlin, S. C. Critchlow and J. A. Kovacs, *Inorg. Chem.*, 1993, **32**, 5868; (e) D. C. Goodman, P. J. Farmer, M. Y. Darensbourg and J. H. Reibenspies, *Inorg. Chem.*, 1996, **35**, 4989 and references therein. For examples of paramagnetic square pyramidal Ni(II) complexes see; (f) S. Brooker and P. D. Croucher, *Chem. Commun.*, 1997, 459; (g) U. Lehmann, J. Lach, C. Loose, T. Hahn, B. Kersting and J. Kortus, *Dalton Trans.*, 2013, **42**, 987.
- W. H. Press, S. A. Teukolsky, W. T. Vetterling and B. P. Flannery, *Numerical Recipes in C: The Art of Scientific Computing*, Cambridge University Press, Cambridge, 2nd edn, 1992.
- (a) K. K. Nanda, L. K. Thomson, J. N. Bridson and K. Nag, *J. Chem. Soc., Chem. Commun.*, 1994, 1337–1338; (b) K. K. Nanda, R. Das, L. K. Thomson, K. Venkatsubramanian, P. Paul and K. Nag, *Inorg. Chem.*, 1994, **33**, 1188–1193; (c) K. K. Nanda, R. Das, L. K. Thomson, K. Venkatsubramanian and K. Nag, *Inorg. Chem.*, 1994, **33**, 5934–5939; (d) A. J. Stemmler, J. W. Kampf, M. L. Kirk and V. L. Pecoraro, *J. Am. Chem. Soc.*, 1995, **117**, 6368–6369; (e) D. Arnold, D. A. Brown, O. Deeg, W. Errington, W. Haase, K. Herlihy, T. J. Kemp, H. Nimir and R. Werner, *Inorg. Chem.*, 1998, **37**, 2920–2925.
- B. Biswas, U. Pieper, T. Weyhermuller and P. Chaudhuri, *Inorg. Chem.*, 2009, **48**, 6781–6793.
- A. Upadhyay, J. Rajpurohit, M. K. Singh, R. Dubey, A. K. Srivastava, A. Kumar, G. Rajaraman and M. Shanmugam, *Chem.-Eur. J.*, 2014, **20**, 6061–6070.
- G. M. Sheldrick, *Acta Crystallogr., Sect. A: Found. Crystallogr.*, 1990, **46**, 467.
- G. M. Sheldrick, *SHELXL-97, A computer programme for crystal structure determination*, University of Gottingen, 1997.
- P. McArdle, P. Daly and D. Cunningham, *J. Appl. Crystallogr.*, 2002, **35**, 378.

- 19 (a) A. Spek, *J. Appl. Crystallogr.*, 2003, **36**, 7–13; (b) P. van der Sluis and A. L. Spek, *Acta Crystallogr., Sect. A: Found. Crystallogr.*, 1990, **46**, 194–201.
- 20 M. J. Frisch, G. W. Trucks, H. B. Schlegel, G. E. Scuseria, M. A. Robb, J. R. Cheeseman, G. Scalmani, V. Barone, B. Mennucci, G. A. Petersson, H. Nakatsuji, M. Caricato, X. Li, H. P. Hratchian, A. F. Izmaylov, J. Bloino, G. Zheng, J. L. Sonnenberg, M. Hada, M. Ehara, K. Toyota, R. Fukuda, J. Hasegawa, M. Ishida, T. Nakajima, Y. Honda, O. Kitao, H. Nakai, T. Vreven, J. A. Montgomery, J. E. Peralta, F. Ogliaro, M. Bearpark, J. J. Heyd, E. Brothers, K. N. Kudin, V. N. Staroverov, R. Kobayashi, J. Normand, K. Raghavachari, A. Rendell, J. C. Burant, S. S. Iyengar, J. Tomasi, M. Cossi, N. Rega, J. M. Millam, M. Klene, J. E. Knox, J. B. Cross, V. Bakken, C. Adamo, J. Jaramillo, R. Gomperts, R. E. Stratmann, O. Yazyev, A. Austin, J. R. Cammi, C. Pomelli, J. W. Ochterski, R. L. Martin, K. Morokuma, V. G. Zakrzewski, G. A. Voth, P. Salvador, J. J. Dannenberg, S. Dapprich, A. D. Daniels, Ö. Farkas, J. B. Foresman, J. V. Ortiz, J. Cioslowski and D. J. Fox, *Gaussian 09*. 2009.
- 21 (a) A. D. Becke, *J. Chem. Phys.*, 1993, **98**, 5648; (b) A. D. Becke, *J. Chem. Phys.*, 1993, **98**, 1372; (c) C. Lee, W. Yang and R. G. Parr, *Phys. Rev. B: Condens. Matter*, 1988, **37**, 785; (d) P. J. Stephens, F. J. Devlin, C. F. Chabalowski and M. J. Frisch, *J. Phys. Chem.*, 1994, **98**, 11623.
- 22 (a) A. Schaefer, H. Horn and R. Ahlrichs, *J. Chem. Phys.*, 1992, **97**, 2571; (b) A. Schaefer, C. Huber and R. Ahlrichs, *J. Chem. Phys.*, 1994, **100**, 5829; (c) G. E. Scuseria and H. F. Schaefer III, *J. Chem. Phys.*, 1989, **90**, 3700.
- 23 J. J. Borrás-Almenar, J. M. Clemente-Juan, E. Coronado and B. S. Tsukerblat, *J. Comput. Chem.*, 2001, **22**, 985.
- 24 D. Gaynor, Z. A. Starikova, W. Haase and K. B. Nolan, *Dalton Trans.*, 2001, 1578.